

SVENSK STANDARD

SS-EN 15689:2009

Fastställt/Approved: 2009-12-07
Publicerad/Published: 2010-01-15
Utgåva/Edition: 1
Språk/Language: engelska/English
ICS: 93.100

Järnvägar – Spår – Spårväxlar och -korsningar – Korsningskomponenter av gjutet austenitiskt manganstål

Railway applications – Track – Switches and crossings – Crossing components made of cast austenitic manganese steel

This preview is downloaded from www.sis.se. Buy the entire standard via <https://www.sis.se/std-71926>

Hitta rätt produkt och ett leveranssätt som passar dig

Standarder

Genom att följa gällande standard både effektiviserar och säkrar du ditt arbete. Många standarder ingår dessutom ofta i paket.

Tjänster

Abonnemang är tjänsten där vi uppdaterar dig med aktuella standarder när förändringar sker på dem du valt att abonnera på.

På så sätt är du säker på att du alltid arbetar efter rätt utgåva.

e-nav är vår online-tjänst som ger dig och dina kollegor tillgång till standarder ni valt att abonnera på dygnet runt. Med e-nav kan samma standard användas av flera personer samtidigt.

Leveranssätt

Du väljer hur du vill ha dina standarder levererade. Vi kan erbjuda dig dem på papper och som pdf.

Andra produkter

Vi har böcker som underlättar arbetet att följa en standard. Med våra böcker får du ökad förståelse för hur standarder ska följas och vilka fördelar den ger dig i ditt arbete. Vi tar fram många egna publikationer och fungerar även som återförsäljare. Det gör att du hos oss kan hitta över 500 unika titlar. Vi har även tekniska rapporter, specifikationer och "workshop agreement".

Matriser är en översikt på standarder och handböcker som bör läsas tillsammans. De finns på sis.se och ger dig en bra bild över hur olika produkter hör ihop.

Standardiseringsprojekt

Du kan påverka innehållet i framtida standarder genom att delta i någon av SIS ca 400 Tekniska Kommittéer.

Find the right product and the type of delivery that suits you

Standards

By complying with current standards, you can make your work more efficient and ensure reliability. Also, several of the standards are often supplied in packages.

Services

Subscription is the service that keeps you up to date with current standards when changes occur in the ones you have chosen to subscribe to. This ensures that you are always working with the right edition.

e-nav is our online service that gives you and your colleagues access to the standards you subscribe to 24 hours a day. With e-nav, the same standards can be used by several people at once.

Type of delivery

You choose how you want your standards delivered. We can supply them both on paper and as PDF files.

Other products

We have books that facilitate standards compliance. They make it easier to understand how compliance works and how this benefits you in your operation. We produce many publications of our own, and also act as retailers. This means that we have more than 500 unique titles for you to choose from. We also have technical reports, specifications and workshop agreements.

Matrices, listed at sis.se, provide an overview of which publications belong together.

Standardisation project

You can influence the content of future standards by taking part in one or other of SIS's 400 or so Technical Committees.

Europastandarden EN 15689:2009 gäller som svensk standard. Detta dokument innehåller den officiella engelska versionen av EN 15689:2009.

The European Standard EN 15689:2009 has the status of a Swedish Standard. This document contains the official English version of EN 15689:2009.

© Copyright/Upphovsrätten till denna produkt tillhör SIS, Swedish Standards Institute, Stockholm, Sverige. Användningen av denna produkt regleras av slutanvändarlicensen som återfinns i denna produkt, se standardens sista sidor.

© Copyright SIS, Swedish Standards Institute, Stockholm, Sweden. All rights reserved. The use of this product is governed by the end-user licence for this product. You will find the licence in the end of this document.

Upplysningar om sakinnehållet i standarden lämnas av SIS, Swedish Standards Institute, telefon 08-555 520 00.

Standarder kan beställas hos SIS Förlag AB som även lämnar allmänna upplysningar om svensk och utländsk standard.

Information about the content of the standard is available from the Swedish Standards Institute (SIS), tel +46 8 555 520 00.

Standards may be ordered from SIS Förlag AB, who can also provide general information about Swedish and foreign standards.

SIS Förlag AB, SE 118 80 Stockholm, Sweden. Tel: +46 8 555 523 10. Fax: +46 8 555 523 11.

E-mail: sis.sales@sis.se Internet: www.sis.se

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 15689

November 2009

ICS 93.100

English Version

Railway applications - Track - Switches and crossings - Crossing components made of cast austenitic manganese steel

Applications ferroviaires - Voie - Appareils de voie - Coeurs
ou composants de coeur en acier moulé au manganèse

Bahnanwendungen - Oberbau - Weichen und Kreuzungen -
Gegossener austenitischer Manganstahl für
Herzstückbauteile

This European Standard was approved by CEN on 10 October 2009.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents		Page
Foreword.....		3
1	Scope	4
2	Normative references	4
3	Terms and definitions	5
4	Quality systems	5
5	Sample approval	5
6	General requirements.....	6
6.1	Materials (liquid chemistry)	6
6.2	Microstructure.....	6
6.3	Surface conditions.....	6
6.3.1	Un-machined and heat treated surfaces	6
6.3.2	Definition of surface zones.....	7
6.3.3	Machined surfaces.....	7
6.3.4	Tolerances	7
6.4	Internal soundness	8
6.4.1	General.....	8
6.4.2	Definition of zones and acceptance levels	8
6.4.3	Frequency for radiographic examination	12
6.5	Foundry practice.....	12
7	Acceptance tests	13
7.1	Chemical analysis.....	13
7.2	Impact bend.....	13
7.3	Metallographic examination	13
7.4	Visual inspection	13
7.5	Dye penetrant testing	13
7.6	Radiography.....	14
7.6.1	General.....	14
7.6.2	Method of radiography.....	14
8	Additional requirements for pre-hardened crossings	14
8.1	Qualification	14
8.1.1	Generally.....	14
8.1.2	Dye penetration test	14
8.1.3	Hardness requirements.....	14
8.2	Production tests.....	16
8.3	Monitoring of pre-hardening process.....	16
9	Weld rectification of surface discontinuities	16
9.1	Qualification of the weld procedure and the welder	16
9.2	Definition of rectification zones, max. dimensions of excavations.....	16
9.3	Testing of weld rectification	17
9.4	Welding records.....	17
10	Identification and marking	17
11	Documentation.....	18
12	Non-common cast manganese crossings	18
Bibliography		19

Foreword

This document (EN 15689:2009) has been prepared by Technical Committee CEN/TC 256 "Railway applications", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2010, and conflicting national standards shall be withdrawn at the latest by May 2010.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This European Standard is complementary to the series of standards EN 13232 "*Railway applications — Track — Switches and crossings*", which covers the design and quality of switches and crossings in flat bottomed rail.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

The scope of this European Standard is:

- to establish material requirements for cast austenitic manganese steel for fixed crossings and cradles for crossings with moveable parts designed to be welded or bolted to rails;
- to formulate codes of practice for inspection, testing of un-machined and machined heat-treated castings;
- to list the methods by which crossings should be identified and traced;
- to define limits of weld rectification by the supplier;
- special requirements for pre-hardened crossings.

Geometrical aspects, as machining tolerances and inspection of finished crossings are covered in EN 13232-6 and EN 13232-7 and therefore not in this European Standard.

This European Standard specifies the minimum requirements for cast manganese crossing components. Special applications (for instance tram systems) can require different demands in certain paragraphs and need to be agreed between customer and supplier.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 444:1994, *Non-destructive testing — General principles for the radiographic examination of metallic materials using X- and gamma-rays*

EN 462-3:1996, *Non-destructive testing — Image quality of radiographs — Part 3: Image quality classes for ferrous metals*

EN 473:2008, *Non destructive testing — Qualification and certification of NDT personnel — General principles*

EN 571-1, *Non destructive testing — Penetrant testing — Part 1: General principles*

EN 1370, *Founding — Surface roughness inspection by visual/tactile comparators*

EN 1371-1, *Founding — Liquid penetrant inspection — Part 1: Sand, gravity die and low pressure die castings*

EN 10204, *Metallic products — Types of inspection documents*

EN 13232-1:2003, *Railway applications — Track — Switches and crossings — Part 1: Definitions*

EN 13232-6:2005, *Railway applications — Track — Switches and crossings — Part 6: Fixed common and obtuse crossings*

EN 13232-7:2006, *Railway applications — Track — Switches and crossings — Part 7: Crossings with moveable parts*

EN ISO 11970, *Specification and approval of welding procedures for production welding of steel castings (ISO 11970:2001)*

ISO 8062, *Castings — System of dimensional tolerances and machining allowances*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in 7.4 and 7.5 of EN 13232-1:2003, 3.1 of EN 13232-6:2005, Clause 4 of EN 13232-7:2006 and the following apply.

3.1

weldable crossing

crossing with rail ends suitable for welding into track

3.2

fishplated crossing

crossing with rail ends suitable for mechanical joints

3.3

pre hardened

contact area and running table which is intentionally hardened prior to installation in track

3.4

chaplet

metallic core support that remains in finished part

3.5

customer

operator or user of the equipment, or the purchaser of the equipment on the user's behalf

3.6

supplier

body responsible for the use of the EN in response to the customer's requirements

4 Quality systems

The supplier responsible for the manufacture of the crossing shall be certified by an accredited third party and have an audited quality system or shall have a quality system approved by the customer.

5 Sample approval

The suitability of the pattern design, mould preparation procedures, casting conditions and heat treatment procedures shall be demonstrated by producing prototype casting for every new pattern.

Sample approval by the supplier is necessary for every new pattern. Any subsequent modifications in the manufacturing process, which may influence the quality of the components, shall be the responsibility of the cast foundry to test and record. The customer shall have the right to have access to these records.

All tests according to Clause 7 shall be performed for sample approval. However, radiography may be dispensed with by the customer, in which case this shall be specified in the tender documents.

6 General requirements

6.1 Materials (liquid chemistry)

Table 1 — Materials (liquid chemistry)

Element	Percentage weight components
	Weight %
Carbon	0,95 to 1,3 ^a
Silicon	0,65 max.
Manganese	11,5 to 14,0 ^a
Phosphorus	0,050 max.
Sulphur	0,030 max.
Nickel	1,75 max.
Molybdenum	0,75 max.
Chromium	0,50 max.
Copper	0,30 max.
Aluminium	0,045 max.
^a Manganese shall not be less than 10 times the carbon content.	

Other alloying elements shall not be added.

6.2 Microstructure

Crossing shall have an austenitic microstructure and be free of detrimental carbide precipitation. To prove the as-cast carbidic structure has changed to an acceptable austenitic structure this shall be demonstrated by metallographic examination or mechanical testing (see Clause 7).

6.3 Surface conditions

6.3.1 Un-machined and heat treated surfaces

The minimum level of surface finish shall be as specified in Table 2 with the relevant SCRATA comparators (refer to EN 1370).

Table 2 — Inspection zones

Inspection zone	Ai	Aii	Aiii	Bi	Bii	Biii
Surface finish	A2	A2	A3	A2	A2	A4
Surface inclusions	B2	B2	B4	B2	B2	B5
Gas porosity	C2	C2	C3	C2	C1	C4
Laps and cold shuts	D1	D1	D2	D2	D1	D5
Scabs	E3	E3	E5	E3	E3	E5
Welds	J1	J1	J1	J1	J1	J1

6.3.2 Definition of surface zones

The definition of surface zones is as shown in Figure 1.

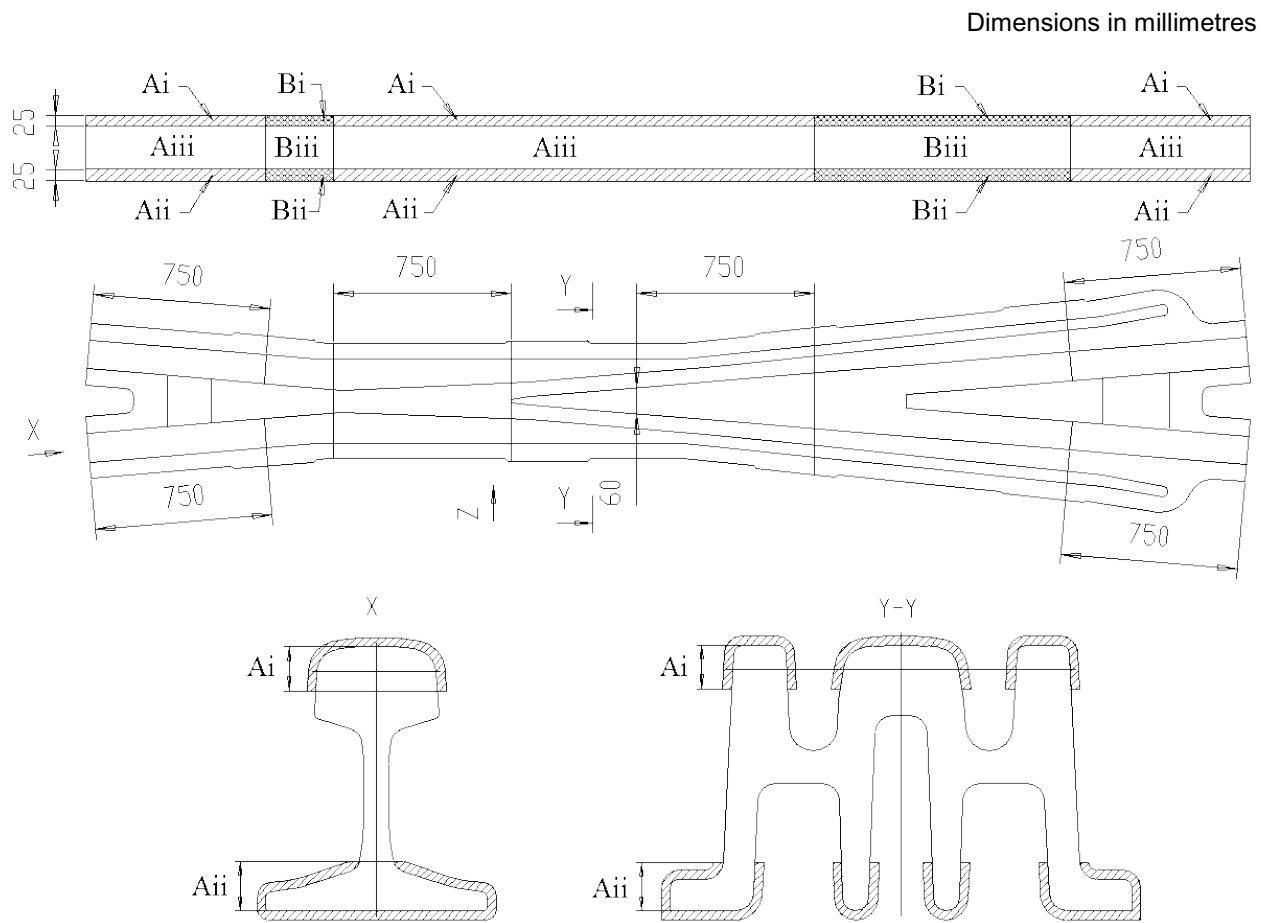


Figure 1 — Definition of surface zones

6.3.3 Machined surfaces

The maximum levels of arithmetical roughness are:

- wheel contact area: Ra 6,3 μm ;
- surfaces without wheel contact: Ra 12,5 μm ;
- fishplate areas: Ra 6,3 μm .

6.3.4 Tolerances

Dimensions of non-machined areas of the casting areas shall comply with tolerances given by ISO 8062 – CT11 unless otherwise agreed between the customer and supplier.

Dimensional tolerances for machined castings shall be referenced on detail drawings for the crossing component. Basic dimensional requirements are given in EN 13232-6 and EN 13232-7.