

SVENSK STANDARD

SS-EN 13144:2018



Fastställt/Approved: 2018-12-04
Utgåva/Edition: 2
Språk/Language: engelska/English
ICS: 25.220.40;25.220.99

Oorganiska ytbeläggningar – Metod att mäta vidhäftning genom dragprovning

Metallic and other inorganic coatings – Method for quantitative measurement of adhesion by tensile test

This preview is downloaded from www.sis.se. Buy the entire standard via <https://www.sis.se/std-80008163>

Standarder får världen att fungera

SIS (Swedish Standards Institute) är en fristående ideell förening med medlemmar från både privat och offentlig sektor. Vi är en del av det europeiska och globala nätverk som utarbetar internationella standarder. Standarder är dokumenterad kunskap utvecklad av framstående aktörer inom industri, näringsliv och samhälle och befrämjar handel över gränser, bidrar till att processer och produkter blir säkrare samt effektiviserar din verksamhet.

Delta och påverka

Som medlem i SIS har du möjlighet att påverka framtida standarder inom ditt område på nationell, europeisk och global nivå. Du får samtidigt tillgång till tidig information om utvecklingen inom din bransch.


Ta del av det färdiga arbetet

Vi erbjuder våra kunder allt som rör standarder och deras tillämpning. Hos oss kan du köpa alla publikationer du behöver – allt från enskilda standarder, tekniska rapporter och standardpaket till handböcker och onlinetjänster. Genom vår webbtjänst e-nav får du tillgång till ett lättnavigerat bibliotek där alla standarder som är aktuella för ditt företag finns tillgängliga. Standarder och handböcker är källor till kunskap. Vi säljer dem.

Utveckla din kompetens och lyckas bättre i ditt arbete

Hos SIS kan du gå öppna eller företagsinterna utbildningar kring innehåll och tillämpning av standarder. Genom vår närhet till den internationella utvecklingen och ISO får du rätt kunskap i rätt tid, direkt från källan. Med vår kunskap om standarders möjligheter hjälper vi våra kunder att skapa verklig nytta och lönsamhet i sina verksamheter.

Vill du veta mer om SIS eller hur standarder kan effektivisera din verksamhet är du välkommen in på www.sis.se eller ta kontakt med oss på tel 08-555 523 00.



Standards make the world go round

SIS (Swedish Standards Institute) is an independent non-profit organisation with members from both the private and public sectors. We are part of the European and global network that draws up international standards. Standards consist of documented knowledge developed by prominent actors within the industry, business world and society. They promote cross-border trade, they help to make processes and products safer and they streamline your organisation.

Take part and have influence

As a member of SIS you will have the possibility to participate in standardization activities on national, European and global level. The membership in SIS will give you the opportunity to influence future standards and gain access to early stage information about developments within your field.

Get to know the finished work

We offer our customers everything in connection with standards and their application. You can purchase all the publications you need from us - everything from individual standards, technical reports and standard packages through to manuals and online services. Our web service e-nav gives you access to an easy-to-navigate library where all standards that are relevant to your company are available. Standards and manuals are sources of knowledge. We sell them.

Increase understanding and improve perception

With SIS you can undergo either shared or in-house training in the content and application of standards. Thanks to our proximity to international development and ISO you receive the right knowledge at the right time, direct from the source. With our knowledge about the potential of standards, we assist our customers in creating tangible benefit and profitability in their organisations.

If you want to know more about SIS, or how standards can streamline your organisation, please visit www.sis.se or contact us on phone +46 (0)8-555 523 00



Europastandarden EN 13144:2018 gäller som svensk standard. Detta dokument innehåller den officiella engelska versionen av EN 13144:2018.

Denna standard ersätter SS-EN 13144, utgåva 1.

The European Standard EN 13144:2018 has the status of a Swedish Standard. This document contains the official version of EN 13144:2018.

This standard supersedes the SS-EN 13144, edition 1.

© Copyright/Upphovsrätten till denna produkt tillhör SIS, Swedish Standards Institute, Stockholm, Sverige. Användningen av denna produkt regleras av slutanvändarlicensen som återfinns i denna produkt, se standardens sista sidor.

© Copyright SIS, Swedish Standards Institute, Stockholm, Sweden. All rights reserved. The use of this product is governed by the end-user licence for this product. You will find the licence in the end of this document.

Upplysningar om sakinnehållet i standarden lämnas av SIS, Swedish Standards Institute, telefon 08-555 520 00. Standarder kan beställas hos SIS som även lämnar allmänna upplysningar om svensk och utländsk standard.

Information about the content of the standard is available from the Swedish Standards Institute (SIS), telephone +46 8 555 520 00. Standards may be ordered from SIS, who can also provide general information about Swedish and foreign standards.

Denna standard är framtagen av kommittén för Oorganiska ytbeläggningar, SIS/TK 116.

Har du synpunkter på innehållet i den här standarden, vill du delta i ett kommande revideringsarbete eller vara med och ta fram andra standarder inom området? Gå in på www.sis.se - där hittar du mer information.

EUROPEAN STANDARD

EN 13144

NORME EUROPÉENNE

EUROPÄISCHE NORM

November 2018

ICS 25.220.40; 25.220.99

Supersedes EN 13144:2003

English Version

Metallic and other inorganic coatings - Method for quantitative measurement of adhesion by tensile test

Revêtements métalliques et autres revêtements inorganiques - Méthode de mesurage quantitatif de l'adhérence par essai de traction

Metallische und andere anorganische Überzüge - Verfahren zur quantitativen Messung der Haftfestigkeit durch den Zugversuch

This European Standard was approved by CEN on 28 September 2018.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

SS-EN 13144:2018 (E)

Contents		Page
European foreword		3
1	Scope	4
2	Normative references	4
3	Terms and definitions	4
4	Determination of adhesive strength by measurement	5
4.1	Principle	5
4.2	Testing devices	5
4.3	Adherend preparation	8
4.4	Adhesives and their application	8
4.5	Test assemblies	9
4.6	Measurement	11
5	Expression of results	12
5.1	Adhesive strength	12
5.2	Failure pattern	12
6	Test report	14
7	Adhesion appraisal test	14
Bibliography		15

European foreword

This document (EN 13144:2018) has been prepared by Technical Committee CEN/TC 262 “Metallic and other inorganic coatings, including for corrosion protection and corrosion testing of metals and alloys”, the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2019 and conflicting national standards shall be withdrawn at the latest by May 2019.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 13144:2003.

In comparison with EN 13144:2003, the following modifications have been made:

- the Scope has been rewritten to give more information;
- normative references have been added;
- the terms and definitions have been updated;
- in addition to the tensile testing machine previously described, the centrifuge has been added as a further type of testing machine;
- sample description has been expanded to describe test stamps, planar samples and coated samples;
- consideration of adhesives and their application has been expanded;
- the measurement section has been revised;
- the expression of results clause has been revised and failure pattern according to EN ISO 10365:1995 added;
- the test report clause has been revised.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

SS-EN 13144:2018 (E)

1 Scope

This document specifies a quantitative method for the measurement of adhesive strength of metallic and other inorganic coatings applied to metallic, polymer and glass substrates.

Typical coatings for which this document applies are metallic coatings such as aluminium, copper, nickel, nickel plus chromium, silver, tin, tin-nickel alloys, zinc, gold as well as other inorganic coatings such as oxides or nitrides, e.g. of aluminium, indium and indium-tin, silicon, niobium, titanium, tungsten, zirconium and others.

This document does not apply to certain hot dip, spray and mechanical coatings, for which other standards may apply, e.g. EN ISO 14916 or EN ISO 4624.

The measurement is valid if the cohesion and adhesion properties of the adhesive are higher than those of the coating subjected to test.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 15870, *Adhesives - Determination of tensile strength of butt joints (ISO 6922:1987 modified)*

EN ISO 4624, *Paints and varnishes - Pull-off test for adhesion (ISO 4624)*

EN ISO 10365:1995, *Adhesives - Designation of main failure patterns (ISO 10365:1992)*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1 adhesive strength

force per unit area required to separate a coating from its substrate

Note 1 to entry: Adhesion can be deemed inadequate in the presence of blisters, scaling and any defect that results from the separation of the coating from its substrate.

3.2 adhesion

physical property resulting from the magnitude of forces joining the atoms and/or molecules at an interface of two materials

3.3 cohesion

physical property resulting from the magnitude of forces joining the atoms and/or molecules within one material

3.4 test block

metallic cylinder used for pull-off tests within the tensile testing machine (described in 4.2.1.2)

3.5

test stamp

metallic disc or cylinder used for pull-off tests within the tensile testing machine (described in 4.2.1.3) or centrifuge (described in 4.2.2.2)

3.6

substrate

base material to which the coating material is applied or is to be applied

Note 1 to entry: Real substrate from the production process or reference substrate of different material coated in the production process or test block of steel coated in the production process.

3.7

sample

coating/substrate system under test as used within the tensile testing machine or centrifuge as counterpart either of test blocks (3.4) or test stamps (3.5)

4 Determination of adhesive strength by measurement

4.1 Principle

The tensile strength required to separate the coating from its substrate is measured perpendicular to the substrate.

The result of the measurement is influenced not only by the mechanical properties of the system to be characterized, but also by the nature and preparation of the substrate.

The result of the measurement can also be affected by internal stress in the coating, which influences adhesion.

The result of the measurement is the tensile strength required to break the weakest interface or the weakest constituent of the test assembly. A combination of both adhesive and cohesive ruptures can also occur. A detailed description and designation of failure patterns is provided in 5.2 and in Table 1.

4.2 Testing devices

4.2.1 Tensile testing machine


4.2.1.1 General

A single-sample testing device that requires a two-sided sample clamping and usually a double cardanic suspension realized by means of ball joints.

It shall be capable of being used in accordance with 4.6. The tensile testing machine is operated either in the force- or path-controlled mode.

NOTE Suitable set-ups for the application of the tensile force are shown in Figure 1.

SS-EN 13144:2018 (E)

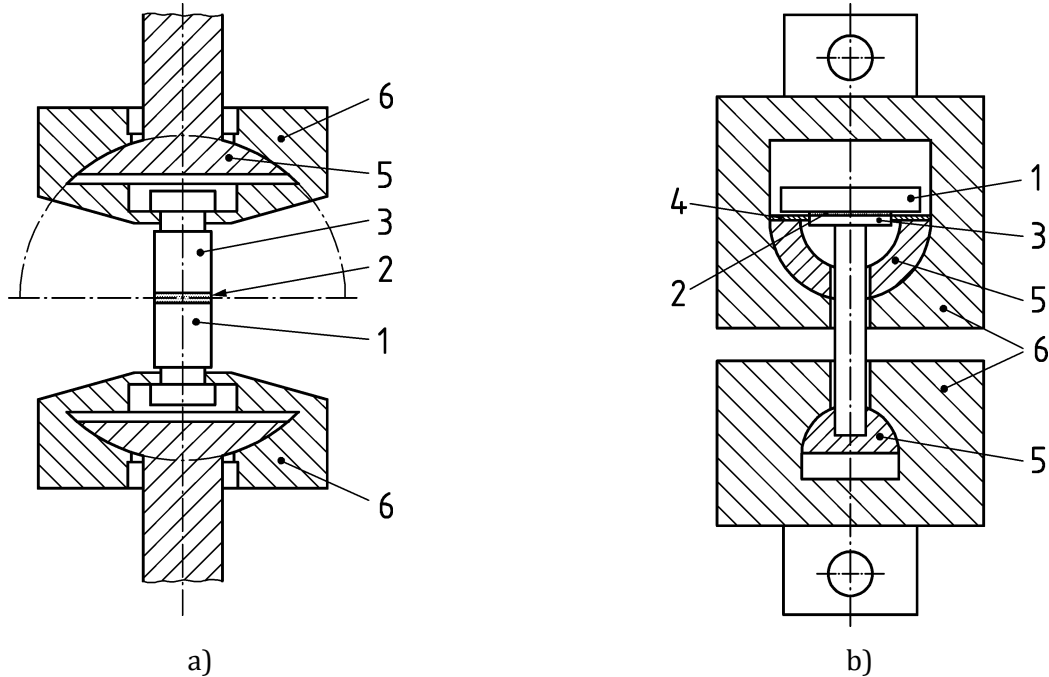

Key

- 1 sample
- 2 adhesive
- 3 test block (Figure 1a)/test stamp (Figure 1b)
- 4 sample support
- 5 ball joint
- 6 suspension

Figure 1 — Set-ups for the application of the tensile force (tensile testing machine)

4.2.1.2 Test blocks

Test blocks shall be made of machined steel, having a cylindrical shape and a diameter of 20 mm, 10 mm or 7 mm in accordance with EN 15870 and EN ISO 4624 (unless otherwise agreed upon).

The thickness of the test block shall be not less than 10 mm to ensure the absence of deformations during the test. Prior to use, the faces acting as adherend shall be machined perpendicular to the major axis of the block.

4.2.1.3 Test stamps

Test stamps may be monolithic or modular. They shall be made of machined steel or other metals. In the case of monolithic test stamps, clamping body and adherend are one piece made from the same material. In the case of modular test stamps, clamping body and adherend are separate, but connectable pieces and can be made from different materials. The adherend diameters shall be 20 mm, 10 mm or 7 mm in accordance with EN 15870 and EN ISO 4624 (unless otherwise agreed upon).

Prior to use, the face acting as adherend shall be machined perpendicular to the major axis of the test stamp.

4.2.1.4 Planar samples

Coated substrate under consideration with diameters or size above the diameter of the test block or test stamp. Except for component geometry, the sample represents the interface of coating and substrate as processed and adhesive strength is tested as shown in set-ups according to Figure 1a) and 1b) and assemblies of Figures 3 and 4.

4.2.1.5 Coated test blocks

Alternatively to using planar samples (4.2.1.4), it is also possible to coat test blocks (4.2.1.2) and use them as samples to be tested. Adhesive strength is tested as shown in a set-up according to Figure 1a) and an assembly according to Figure 5.

4.2.2 Centrifuge


4.2.2.1 General

A multiple-sample testing device for the tensile test that requires a one-sided sample support.

It shall be capable of being used in accordance with 4.6. The centrifuge is operated in the force-controlled mode.

In combination with the coating/substrate system (acting as planar sample 4.2.2.3) and a monolithic or modular test stamp bonded on the coating/substrate system, a guiding sleeve acts both as sample support and as test stamp guidance. The guiding sleeve can also be used as adhesive application kit prior to testing. Thus, any shear force at testing can be avoided and the centrifugal force is used as normal testing force.

NOTE A suitable set-up for the application of the tensile force is shown in Figure 2.

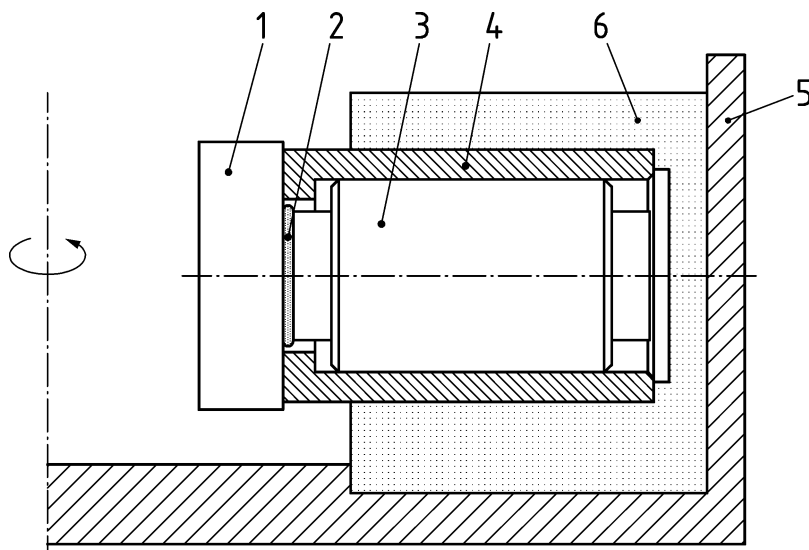

Key

- | | |
|--------------|---------------------------------|
| 1 sample | 4 guiding sleeve/sample support |
| 2 adhesive | 5 drum-rotor |
| 3 test stamp | 6 detection module |

Figure 2 — Set-up for the application of the tensile force (centrifuge)