

SVENSK STANDARD

SS-EN 17224:2019



Fastställt/Approved: 2019-07-15
Utgåva/Edition: 1
Språk/Language: engelska/English
ICS: 83.180

Bestämning av tryck-skjuvspänning av trälim vid höga temperaturer

Determination of compressive shear strength of wood adhesives at elevated temperatures

This preview is downloaded from www.sis.se. Buy the entire standard via <https://www.sis.se/std-80012870>

Standarder får världen att fungera

SIS (Swedish Standards Institute) är en fristående ideell förening med medlemmar från både privat och offentlig sektor. Vi är en del av det europeiska och globala nätverk som utarbetar internationella standarder. Standarder är dokumenterad kunskap utvecklad av framstående aktörer inom industri, näringsliv och samhälle och befrämjar handel över gränser, bidrar till att processer och produkter blir säkrare samt effektiviserar din verksamhet.

Delta och påverka

Som medlem i SIS har du möjlighet att påverka framtida standarder inom ditt område på nationell, europeisk och global nivå. Du får samtidigt tillgång till tidig information om utvecklingen inom din bransch.

Ta del av det färdiga arbetet

Vi erbjuder våra kunder allt som rör standarder och deras tillämpning. Hos oss kan du köpa alla publikationer du behöver – allt från enskilda standarder, tekniska rapporter och standardpaket till handböcker och onlinetjänster. Genom vår webbtjänst e-nav får du tillgång till ett lättnavigerat bibliotek där alla standarder som är aktuella för ditt företag finns tillgängliga. Standarder och handböcker är källor till kunskap. Vi säljer dem.

Utveckla din kompetens och lyckas bättre i ditt arbete

Hos SIS kan du gå öppna eller företagsinterna utbildningar kring innehåll och tillämpning av standarder. Genom vår närhet till den internationella utvecklingen och ISO får du rätt kunskap i rätt tid, direkt från källan. Med vår kunskap om standarders möjligheter hjälper vi våra kunder att skapa verklig nytta och lönsamhet i sina verksamheter.

Vill du veta mer om SIS eller hur standarder kan effektivisera din verksamhet är du välkommen in på www.sis.se eller ta kontakt med oss på tel 08-555 523 00.



Standards make the world go round

SIS (Swedish Standards Institute) is an independent non-profit organisation with members from both the private and public sectors. We are part of the European and global network that draws up international standards. Standards consist of documented knowledge developed by prominent actors within the industry, business world and society. They promote cross-border trade, they help to make processes and products safer and they streamline your organisation.

Take part and have influence

As a member of SIS you will have the possibility to participate in standardization activities on national, European and global level. The membership in SIS will give you the opportunity to influence future standards and gain access to early stage information about developments within your field.

Get to know the finished work

We offer our customers everything in connection with standards and their application. You can purchase all the publications you need from us - everything from individual standards, technical reports and standard packages through to manuals and online services. Our web service e-nav gives you access to an easy-to-navigate library where all standards that are relevant to your company are available. Standards and manuals are sources of knowledge. We sell them.

Increase understanding and improve perception

With SIS you can undergo either shared or in-house training in the content and application of standards. Thanks to our proximity to international development and ISO you receive the right knowledge at the right time, direct from the source. With our knowledge about the potential of standards, we assist our customers in creating tangible benefit and profitability in their organisations.

If you want to know more about SIS, or how standards can streamline your organisation, please visit www.sis.se or contact us on phone +46 (0)8-555 523 00



Europastandarden EN 17224:2019 gäller som svensk standard. Detta dokument innehåller den officiella engelska versionen av EN 17224:2019.

The European Standard EN 17224:2019 has the status of a Swedish Standard. This document contains the official version of EN 17224:2019.

© Copyright/Upphovsrätten till denna produkt tillhör SIS, Swedish Standards Institute, Stockholm, Sverige. Användningen av denna produkt regleras av slutanvändarlicensen som återfinns i denna produkt, se standardens sista sidor.

© Copyright SIS, Swedish Standards Institute, Stockholm, Sweden. All rights reserved. The use of this product is governed by the end-user licence for this product. You will find the licence in the end of this document.

Upplysningar om sakinnehållet i standarden lämnas av SIS, Swedish Standards Institute, telefon 08-555 520 00. Standarder kan beställas hos SIS som även lämnar allmänna upplysningar om svensk och utländsk standard.

Information about the content of the standard is available from the Swedish Standards Institute (SIS), telephone +46 8 555 520 00. Standards may be ordered from SIS, who can also provide general information about Swedish and foreign standards.

Denna standard är framtagen av kommittén för Lim och limningsteknik, SIS/TK 162.

Har du synpunkter på innehållet i den här standarden, vill du delta i ett kommande revideringsarbete eller vara med och ta fram andra standarder inom området? Gå in på www.sis.se - där hittar du mer information.

EUROPEAN STANDARD

EN 17224

NORME EUROPÉENNE

EUROPÄISCHE NORM

July 2019

ICS 83.180

English Version

Determination of compressive shear strength of wood adhesives at elevated temperatures

Détermination de la résistance des adhésifs de bois au cisaillement par compression à températures élevées

Bestimmung der Druck-Scherfestigkeit von Holzklebstoffen bei erhöhten Temperaturen

This European Standard was approved by CEN on 26 May 2019.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

SS-EN 17224:2019 (E)

Contents	Page
European foreword.....	2
Introduction	4
1 Scope.....	5
2 Normative references.....	5
3 Terms and definitions	5
4 Principle	5
5 Apparatus.....	5
5.1 Test jig.....	5
5.2 Climate chamber or oven	5
5.3 Thermocouples	6
5.4 Testing machine	6
6 Test specimens.....	6
6.1 Selection of wood	6
6.2 Preparation of test pieces	6
7 Test procedure	9
7.1 Test at ambient temperature.....	9
7.2 Test at elevated temperature	10
7.3 Evaluation of result	11
8 Expression of results and test report.....	12
Bibliography.....	13

European foreword

This document (EN 17224:2019) has been prepared by Technical Committee CEN/TC 193 “Adhesives”, the secretariat of which is held by UNE.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2020, and conflicting national standards shall be withdrawn at the latest by January 2020.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

SS-EN 17224:2019 (E)

Introduction

Safety statement

Persons using this document should be familiar with the normal laboratory practice, if applicable. This document cannot address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any regulatory conditions.

Environmental statement

It is understood that some of the material permitted in this document can have negative environmental impact. As technological advantages lead to better alternatives for these materials, they will be eliminated from this document to the extent possible.

At the end of the test, the user of the document should take care to carry out an appropriate disposal of the wastes, according to local regulation.

1 Scope

This document specifies a test method for determining the comparative compression shear strength of adhesive bonds and solid wood at both ambient temperature and elevated temperature. The maximum load of the test pieces at ambient temperature and after exposure to a specific elevated temperature for a specified duration of time is evaluated. It is applicable to adhesives used in load bearing timber structures and to other wood adhesives.

This method is intended primarily to obtain performance data for the influence of elevated temperatures on the behaviour of adhesive bonds.

This method is not intended to provide data for structural design, and does not necessarily represent the performance of the bonded element in service.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 923, *Adhesives — Terms and definitions*

EN 14080:2013, *Timber structures — Glued laminated timber and glued solid timber — Requirements*

3 Terms and definitions

For the purposes of this document the terms and definitions given in EN 923 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Principle

Solid wood test pieces and adhesively bonded test pieces are prepared. Both types of test pieces are tested in a compression shear test according to EN 14080:2013, Annex D at ambient temperature and after exposure to an elevated temperature. The compression shear strength of the solid wood test pieces and the adhesively bonded test pieces at ambient temperature and elevated temperature is compared in order to evaluate the shear strength of the adhesive at elevated temperature.

5 Apparatus

5.1 Test jig

The test equipment described in EN 14080:2013, Annex D is suitable for the performance of the shear test.

5.2 Climate chamber or oven

A climate chamber or oven capable of maintaining the targeted temperature to within ± 2 °C and with sufficient air circulation to provide constant temperature conditions within the oven interior for the heating of the test pieces.

SS-EN 17224:2019 (E)

5.3 Thermocouples

Thermocouples capable of measuring the temperature in the test pieces to within ± 2 °C.

5.4 Testing machine

A testing machine capable of performing the block shear test specified in EN 14080:2013, Annex D with an accuracy of ± 1 % of the maximum load is required for the performance of the shear tests.

6 Test specimens

6.1 Selection of wood

In general, Norway spruce (*Picea abies* L.) with a density of (450 ± 25) kg/m³ at 12 % moisture content is used. The test with Norway spruce also covers Silver fir (*Abies alba*) and Scots pine (*Pinus sylvestris*). The use of other wood species is possible.

NOTE When using other wood species, the test results are considered to be representative of the density range used in the test. It is assumed that the results apply to lower densities as well.

The material shall be straight-grained and free from knots, reaction wood, machining defects (such as chipped grain, dubbed ends, feed roll polish, coarse knife marks and feed roll compression) and any drying defects such as case hardening, collapse, splits or checks. The raw material for the preparation of the test pieces shall have dimensions of at least 150 mm (width) × 50 mm (height) and a length of at least 300 mm.

The angle of the annual rings to the surface, as measured from the wide face, shall be between 45° and 90°.


When testing adhesives used in load-bearing timber structures, the wood shall be conditioned at (20 ± 2) °C and a relative humidity of (65 ± 5) % until a moisture content of (12 ± 1) % has been obtained.

When testing wood adhesives for non-load-bearing applications, the wood may alternatively be conditioned at (23 ± 2) °C and a relative humidity of (50 ± 5) % until equilibrium moisture content is obtained.

Plane each lamination not more than 8 h before the bonding of the test pieces.

6.2 Preparation of test pieces

Solid wood block shear test pieces and adhesively bonded block shear test pieces shall be produced. To ensure that all test pieces have a comparable wood quality, the solid wood test pieces and the adhesively bonded test pieces shall be produced using the same raw material following the principle as shown in Figure 1. At least four test pieces, two solid wood test pieces for testing at ambient temperature and elevated temperature and two adhesively bonded test pieces for testing at ambient temperature and elevated temperature, shall be produced from one board.

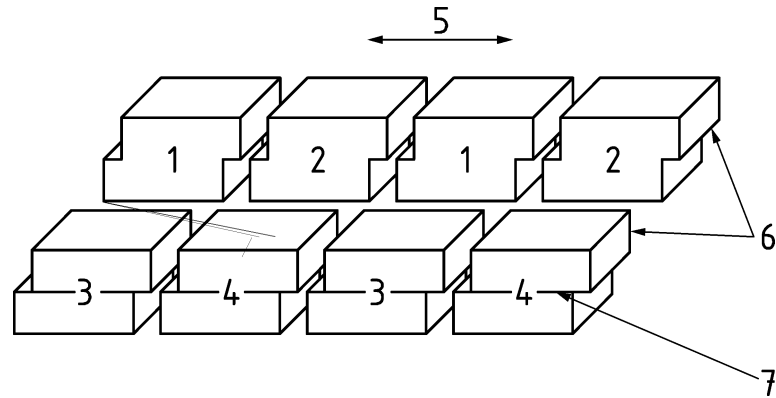


Key

- | | | | |
|---|------------------------------|---|------------------------|
| 1 | solid, ambient temperature | 5 | grain direction |
| 2 | solid, elevated temperature | 6 | side-matched specimens |
| 3 | bonded, ambient temperature | 7 | bondline |
| 4 | bonded, elevated temperature | | |

Figure 1 — Principle for production of side-matched test pieces

20 bonded test pieces shall be prepared in accordance with Figure 2. In addition, 20 solid wood control test pieces shall be produced with the same dimensions as the bonded test pieces. The bonded test pieces and the matched solid wood test pieces shall be produced as 20 pairs. Care shall be taken to ensure the same annual ring orientation when bonding the laminations together into a bonded assembly.

Dimensions in millimetres

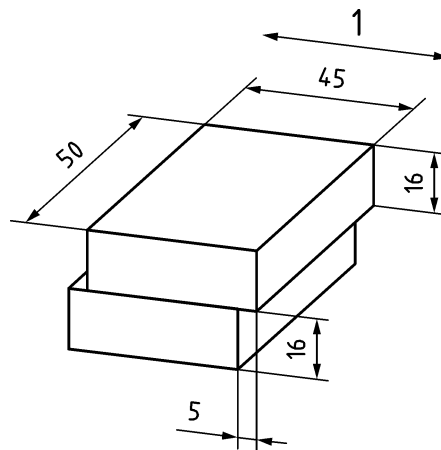

Key

- 1 grain direction

Figure 2 — Form and dimensions of the final block shear test pieces

The bonded test pieces shall be prepared from laminations (16,0 ± 0,1) mm thick (after planing) by (60,0 ± 0,1) mm wide. The adhesive preparation and the bonding procedure shall follow the adhesive manufacturer's recommendation.