

SVENSK STANDARD

SS-EN ISO 17872:2019



Fastställt/Approved: 2019-10-07
Utgåva/Edition: 2
Språk/Language: engelska/English
ICS: 77.060; 87.040

Färg och lack – Riktlinjer för införande av repor genom beläggningar på provplåtar av metall före korrosionsprovning (ISO 17872:2019)

Paints and varnishes – Guidelines for the introduction of scribe marks through coatings on metallic panels for corrosion testing (ISO 17872:2019)

This preview is downloaded from www.sis.se. Buy the entire standard via <https://www.sis.se/std-80017406>

Standarder får världen att fungera

SIS (Swedish Standards Institute) är en fristående ideell förening med medlemmar från både privat och offentlig sektor. Vi är en del av det europeiska och globala nätverk som utarbetar internationella standarder. Standarder är dokumenterad kunskap utvecklad av framstående aktörer inom industri, näringsliv och samhälle och befrämjar handel över gränser, bidrar till att processer och produkter blir säkrare samt effektiviserar din verksamhet.

Delta och påverka

Som medlem i SIS har du möjlighet att påverka framtida standarder inom ditt område på nationell, europeisk och global nivå. Du får samtidigt tillgång till tidig information om utvecklingen inom din bransch.

Ta del av det färdiga arbetet

Vi erbjuder våra kunder allt som rör standarder och deras tillämpning. Hos oss kan du köpa alla publikationer du behöver – allt från enskilda standarder, tekniska rapporter och standardpaket till handböcker och onlinetjänster. Genom vår webbtjänst e-nav får du tillgång till ett lättnavigerat bibliotek där alla standarder som är aktuella för ditt företag finns tillgängliga. Standarder och handböcker är källor till kunskap. Vi säljer dem.

Utveckla din kompetens och lyckas bättre i ditt arbete

Hos SIS kan du gå öppna eller företagsinterna utbildningar kring innehåll och tillämpning av standarder. Genom vår närhet till den internationella utvecklingen och ISO får du rätt kunskap i rätt tid, direkt från källan. Med vår kunskap om standarders möjligheter hjälper vi våra kunder att skapa verklig nytta och lönsamhet i sina verksamheter.

Vill du veta mer om SIS eller hur standarder kan effektivisera din verksamhet är du välkommen in på www.sis.se eller ta kontakt med oss på tel 08-555 523 00.



Standards make the world go round

SIS (Swedish Standards Institute) is an independent non-profit organisation with members from both the private and public sectors. We are part of the European and global network that draws up international standards. Standards consist of documented knowledge developed by prominent actors within the industry, business world and society. They promote cross-border trade, they help to make processes and products safer and they streamline your organisation.

Take part and have influence

As a member of SIS you will have the possibility to participate in standardization activities on national, European and global level. The membership in SIS will give you the opportunity to influence future standards and gain access to early stage information about developments within your field.

Get to know the finished work

We offer our customers everything in connection with standards and their application. You can purchase all the publications you need from us - everything from individual standards, technical reports and standard packages through to manuals and online services. Our web service e-nav gives you access to an easy-to-navigate library where all standards that are relevant to your company are available. Standards and manuals are sources of knowledge. We sell them.

Increase understanding and improve perception

With SIS you can undergo either shared or in-house training in the content and application of standards. Thanks to our proximity to international development and ISO you receive the right knowledge at the right time, direct from the source. With our knowledge about the potential of standards, we assist our customers in creating tangible benefit and profitability in their organisations.

If you want to know more about SIS, or how standards can streamline your organisation, please visit www.sis.se or contact us on phone +46 (0)8-555 523 00



Europastandarden EN ISO 17872:2019 gäller som svensk standard. Detta dokument innehåller den officiella engelska versionen av EN ISO 17872:2019.

Denna standard ersätter SS-EN ISO 17872:2007, utgåva 1

The European Standard EN ISO 17872:2019 has the status of a Swedish Standard. This document contains the official version of EN ISO 17872:2019.

This standard supersedes the SS-EN ISO 17872:2007, edition 1

© Copyright/Upphovsrätten till denna produkt tillhör SIS, Swedish Standards Institute, Stockholm, Sverige. Användningen av denna produkt regleras av slutanvändarlicensen som återfinns i denna produkt, se standardens sista sidor.

© Copyright SIS, Swedish Standards Institute, Stockholm, Sweden. All rights reserved. The use of this product is governed by the end-user licence for this product. You will find the licence in the end of this document.

Upplysningar om sakinnehållet i standarden lämnas av SIS, Swedish Standards Institute, telefon 08-555 520 00. Standarder kan beställas hos SIS som även lämnar allmänna upplysningar om svensk och utländsk standard.

Information about the content of the standard is available from the Swedish Standards Institute (SIS), telephone +46 8 555 520 00. Standards may be ordered from SIS, who can also provide general information about Swedish and foreign standards.

Denna standard är framtagen av kommittén för Färg och lack, SIS/TK 433.

Har du synpunkter på innehållet i den här standarden, vill du delta i ett kommande revideringsarbete eller vara med och ta fram andra standarder inom området? Gå in på www.sis.se - där hittar du mer information.

EUROPEAN STANDARD

EN ISO 17872

NORME EUROPÉENNE

EUROPÄISCHE NORM

October 2019

ICS 87.040

Supersedes EN ISO 17872:2007

English Version

Paints and varnishes - Guidelines for the introduction of scribe marks through coatings on metallic panels for corrosion testing (ISO 17872:2019)

Peintures et vernis - Lignes directrices pour la production de rayures au travers du revêtement de panneaux métalliques en vue des essais de corrosion (ISO 17872:2019)

Beschichtungsstoffe - Leitfaden zum Anbringen von Ritzen durch eine Beschichtung auf Metallplatten für Korrosionsprüfungen (ISO 17872:2019)

This European Standard was approved by CEN on 5 August 2019.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

| Contents | | Page |
|---|--|-------------|
| European foreword | | vii |
| Introduction | | viii |
| 1 | Scope | 1 |
| 2 | Normative references | 1 |
| 3 | Terms and definitions | 1 |
| 4 | Scribe marks | 1 |
| 5 | Apparatus | 5 |
| 6 | Test panels | 5 |
| 7 | Procedure | 5 |
| 8 | Verification of the scribing tool | 5 |
| 9 | Report | 6 |
| Annex A (informative) Scribing tools | | 7 |
| Annex B (informative) Examples of possible different results in one corrosion test when using different scribing tools | | 16 |
| Bibliography | | 22 |

European foreword

This document (EN ISO 17872:2019) has been prepared by Technical Committee ISO/TC 35 "Paints and varnishes" in collaboration with Technical Committee CEN/TC 139 "Paints and varnishes" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 2020, and conflicting national standards shall be withdrawn at the latest by April 2020.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 17872:2007.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 17872:2019 has been approved by CEN as EN ISO 17872:2019 without any modification.

Introduction

Many International Standards deal with corrosion testing, where scribe marks are introduced through a coating to a metallic substrate. However, the method of scribe-mark introduction (scribing pattern, tools, etc.) is not standardized across these standards.

The main purposes of an intentionally inflicted damage in a coating prior to corrosion testing are as follows:

- a) to simulate and to investigate how adhesion of a coating originating from an artificial damage after exposure is ensured;
- b) to obtain an accelerated response during a corrosion test, e.g. at quality control during production;
- c) to investigate the general durability of a coating by observation of the rate of corrosion at a damage spread after exposure.

Preliminary investigations have shown that several variants, both in terms of shape and dimensions, of scribing tools are used. These variations occur both across countries and within countries. The effect of using different tools is the production of scribe marks with different cross-sectional shape, depth and exposed metal area. These differences will greatly affect test results obtained during corrosion tests, as the intention of introducing scribe marks into a coating system is such that oxygen and the electrolyte present during exposure testing can obtain access to a well-defined and active metal surface.

The actual method used to introduce a scribe mark depends on the coating type and thickness. However, in all cases it is preferable if the cross-section is as smooth as possible, the metallic substrate is exposed evenly and no coating remains on the exposed substrate.

Paints and varnishes — Guidelines for the introduction of scribe marks through coatings on metallic panels for corrosion testing

1 Scope

This document describes methods of scribing coated steel or test-pieces for corrosion tests, where the coating system is applied at dry film thicknesses of less than 500 µm. It is intended as a guideline only, being based on the results of a collaborative trial with no subsequent corrosion testing having been carried out to determine the suitability of the introduced scribe marks for such tests.

This document covers the scribing of metallic panels or test pieces (chemically treated or not) made from:

- steel;
- galvanized steel;
- aluminium alloys;
- magnesium alloys.

It does not cover the scribing of electroplated metal or clad aluminium panels.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4618, *Paints and varnishes — Terms and definitions*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4618 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Scribe marks

Different scribe marks create different results depending on the used corrosion test.

The scribing method greatly affects how the corrosion process occurs and the reproducibility when tests are repeated under the same conditions. Examples of possible different results in one corrosion test when using different scribing tools are given in [Annex B](#). In order to obtain results with high accuracy and reproducibility, accurate and consistent scribing is required.

If not otherwise agreed or specified, a scribe mark is made as described in [Figure 1a](#)) to [Figure 1e](#)) through the coating to the metal substrate according to the agreed conditions. For hot-dip galvanized steel the scribe shall be cut completely through the paint coating and the metal layer and into the steel substrate, as specified in ISO 12944-6 and ISO 12944-9.

Typically, the suitable length of the scribed lines is in the range of 50 mm to 70 mm, depending on the coating thickness and the expected amount of corrosion. The length of the scribe mark should be

SS-EN ISO 17872:2019 (E)

significantly more than the expected creep resulting from the corrosion test carried out. It should give an overview what happens on the surface of the system. Too short scribing lengths have an impact on the results.

The width of the scribe mark can also affect the result of a corrosion test. The smaller the width, the stronger is the tendency for the exposed metal surface to be passivated by deposition of sparingly soluble corrosion products. Kind and thickness of an organic coating can have an impact to the scribing line in that way that the scribing line closes itself partially in kind of a capillary. Therefore, no or less electrolytes and/or oxygen could reach the metal surface. It is therefore important to select a scribing tool which will provide a suitable scribe width for the corrosion test being carried out.


The orientation of the scribed lines is often significant in terms of affecting corrosion test results. On panels with a slight inclination from the vertical, e.g. for salt-spray tests, more salt is collected in a horizontally exposed scribe mark. Also, a horizontally exposed scribe mark will generate an even salt distribution, whereas a diagonal, or more particularly a vertical, scribe mark tends to generate a gradient, with an increasing amount of salt along the lower edge of the scribe mark. An increased amount of salt usually leads to an increased corrosion rate, but on coated steel, high salt concentration might have an inhibiting effect on corrosion since the formed corrosion products are very dense.

Milled/rolled aluminium substrates shall get basically two scribes in different orientations to consider the influence of the milling/rolling direction to the corrosion result.

The cross-section of the scribe mark should be as uniform as possible along its entire length. The coating should be cut smoothly along the direction of the scribe mark. The cross-sectional shape of the scribe may be either "V" or "U" shaped, depending upon the tool used, and should be such that for a "V"-shaped cut $a > b > c$ and for a "U"-shaped cut $a > b$, with the width (b) of both "V" and "U" shapes such that $b \geq 0,2$ mm (see [Figure 2](#) for an explanation of the symbols). Certain scribing tools can also produce a rectangular cross-section, where a , b and c are approximately equal (one example is the "U"-shaped cut variation 2).


The shape, depth and uniformity of scribe marks resulting from the use of manual scribing tools will also depend on the operator carrying out the scribing procedure. To reduce this operator dependency, and hence variability in subsequent corrosion test results, automatic scribing machines may also be used to introduce scribe marks, provided they produce a scribe mark which penetrates to the substrate. Such machines are able to introduce rectangular shaped scribe marks, where the dimensions a , b and c are approximately equal and each is greater than 0,5 mm.

Dimensions in millimetres

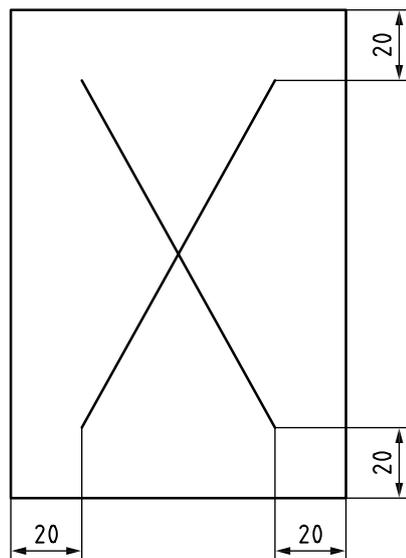


NOTE 1 When evaluating the X-shape scribe in accordance with ISO 4628-8, the section of scribe at the intersection is ignored. Overlapping can happen.

a) X-shape

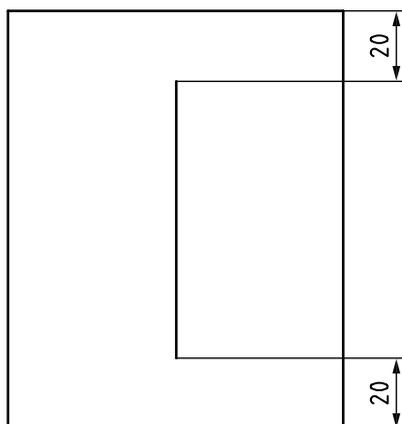

The scribe should be located centrally on the plate to meet the minimum distance of 20 mm to the edge.

b) Single line

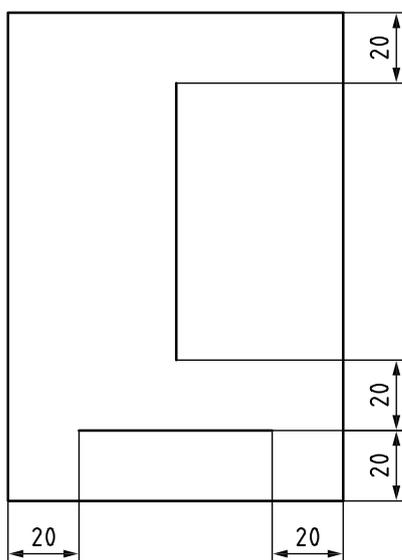

The scribe parallel to the longer side of the panel should be located centrally on the plate to meet the minimum distance of 20 mm to the edge.

c) T-shape