

SVENSK STANDARD

SS-EN 13674-1:2011+A1:2017



Fastställt/Approved: 2017-06-07
Publicerad/Published: 2017-06-08
Utgåva/Edition: 1
Språk/Language: engelska/English
ICS: 45.080; 93.100

Järnvägar – Spår – Räler – Del 1: Vignolräler fr o m 46 kg/m

Railway applications – Track – Rail – Part 1: Vignole railway rails 46 kg/m and above

This preview is downloaded from www.sis.se. Buy the entire standard via <https://www.sis.se/std-8026769>

Standarder får världen att fungera

SIS (Swedish Standards Institute) är en fristående ideell förening med medlemmar från både privat och offentlig sektor. Vi är en del av det europeiska och globala nätverk som utarbetar internationella standarder. Standarder är dokumenterad kunskap utvecklad av framstående aktörer inom industri, näringsliv och samhälle och befrämjar handel över gränser, bidrar till att processer och produkter blir säkrare samt effektiviserar din verksamhet.

Delta och påverka

Som medlem i SIS har du möjlighet att påverka framtida standarder inom ditt område på nationell, europeisk och global nivå. Du får samtidigt tillgång till tidig information om utvecklingen inom din bransch.

Ta del av det färdiga arbetet

Vi erbjuder våra kunder allt som rör standarder och deras tillämpning. Hos oss kan du köpa alla publikationer du behöver – allt från enskilda standarder, tekniska rapporter och standardpaket till handböcker och onlinetjänster. Genom vår webbtjänst e-nav får du tillgång till ett lättnavigerat bibliotek där alla standarder som är aktuella för ditt företag finns tillgängliga. Standarder och handböcker är källor till kunskap. Vi säljer dem.

Utveckla din kompetens och lyckas bättre i ditt arbete

Hos SIS kan du gå öppna eller företagsinterna utbildningar kring innehåll och tillämpning av standarder. Genom vår närhet till den internationella utvecklingen och ISO får du rätt kunskap i rätt tid, direkt från källan. Med vår kunskap om standarders möjligheter hjälper vi våra kunder att skapa verklig nytta och lönsamhet i sina verksamheter.

Vill du veta mer om SIS eller hur standarder kan effektivisera din verksamhet är du välkommen in på www.sis.se eller ta kontakt med oss på tel 08-555 523 00.



Standards make the world go round

SIS (Swedish Standards Institute) is an independent non-profit organisation with members from both the private and public sectors. We are part of the European and global network that draws up international standards. Standards consist of documented knowledge developed by prominent actors within the industry, business world and society. They promote cross-border trade, they help to make processes and products safer and they streamline your organisation.

Take part and have influence

As a member of SIS you will have the possibility to participate in standardization activities on national, European and global level. The membership in SIS will give you the opportunity to influence future standards and gain access to early stage information about developments within your field.

Get to know the finished work

We offer our customers everything in connection with standards and their application. You can purchase all the publications you need from us - everything from individual standards, technical reports and standard packages through to manuals and online services. Our web service e-nav gives you access to an easy-to-navigate library where all standards that are relevant to your company are available. Standards and manuals are sources of knowledge. We sell them.

Increase understanding and improve perception

With SIS you can undergo either shared or in-house training in the content and application of standards. Thanks to our proximity to international development and ISO you receive the right knowledge at the right time, direct from the source. With our knowledge about the potential of standards, we assist our customers in creating tangible benefit and profitability in their organisations.

If you want to know more about SIS, or how standards can streamline your organisation, please visit www.sis.se or contact us on phone +46 (0)8-555 523 00



Europastandarden EN 13674-1:2011+A1:2017 gäller som svensk standard. Detta dokument innehåller den officiella engelska versionen av EN 13674-1:2011+A1:2017.

Denna standard ersätter SS-EN 13674-1:2011, utgåva 2.

The European Standard EN 13674-1:2011+A1:2017 has the status of a Swedish Standard. This document contains the official version of EN 13674-1:2011+A1:2017.

This standard supersedes the Swedish Standard SS-EN 13674-1:2011, edition 2.

© Copyright/Upphovsrätten till denna produkt tillhör SIS, Swedish Standards Institute, Stockholm, Sverige. Användningen av denna produkt regleras av slutanvändarlicensen som återfinns i denna produkt, se standardens sista sidor.

© Copyright SIS, Swedish Standards Institute, Stockholm, Sweden. All rights reserved. The use of this product is governed by the end-user licence for this product. You will find the licence in the end of this document.

Upplysningar om sakinnehållet i standarden lämnas av SIS, Swedish Standards Institute, telefon 08-555 520 00. Standarder kan beställas hos SIS Förlag AB som även lämnar allmänna upplysningar om svensk och utländsk standard.

Information about the content of the standard is available from the Swedish Standards Institute (SIS), telephone +46 8 555 520 00. Standards may be ordered from SIS Förlag AB, who can also provide general information about Swedish and foreign standards.

Denna standard är framtagen av kommittén för Järnvägar, SIS/TK 254.

Har du synpunkter på innehållet i den här standarden, vill du delta i ett kommande revideringsarbete eller vara med och ta fram andra standarder inom området? Gå in på www.sis.se - där hittar du mer information.

EUROPEAN STANDARD

EN 13674-1:2011+A1

NORME EUROPÉENNE

EUROPÄISCHE NORM

May 2017

ICS 93.100

Supersedes EN 13674-1:2011

English Version

Railway applications - Track - Rail - Part 1: Vignole railway rails 46 kg/m and above

Applications ferroviaires - Voie - Rails - Partie 1 : Rails
Vignole de masse supérieure ou égale à 46 kg/m

Bahnwendungen - Oberbau - Schienen - Teil 1:
Vignolschienen ab 46 kg/m

This European Standard was approved by CEN on 10 December 2010 and includes Amendment 1 approved by CEN on 25 December 2016.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

SS-EN 13674-1:2011+A1:2017 (E)

Contents	Page
European foreword.....	5
Introduction	7
1 Scope.....	8
2 Normative references.....	8
3 Terms and definitions	8
4 Information to be supplied by the purchaser.....	9
5 Steel grades	10
6 Profile drawings/properties/mass	11
7 Manufacture	12
7.1 Product integrity.....	12
7.2 Blooms.....	12
7.3 Rails.....	12
7.4 Identification	12
7.4.1 Branding.....	12
7.4.2 Hot stamping.....	13
7.4.3 Cold stamping.....	14
7.4.4 Other identification.....	14
8 Qualifying tests	14
8.1 Procedure.....	14
8.2 Fracture toughness (K_{IC}).....	15
8.2.1 Test pieces and test methods.....	15
8.2.2 Qualifying criteria.....	15
8.3 Fatigue crack growth rate	15
8.3.1 Test method	15
8.3.2 Test pieces	15
8.3.3 Number of tests and test conditions.....	15
8.3.4 Qualifying criteria.....	15
8.4 Fatigue test	16
8.4.1 Test method	16
8.4.2 Test pieces	16
8.4.3 Number of tests and test conditions.....	16
8.4.4 Qualifying criteria.....	16
8.5 Residual stress in rail foot	16
8.5.1 Test method	16
8.5.2 Test pieces	16
8.5.3 Measurements.....	16
8.5.4 Qualifying criteria.....	16
8.6 Variation of centre line running surface hardness of heat treated rails.....	17
8.7 Tensile strength and elongation.....	17
8.8 Segregation.....	18
8.9 Other qualifying requirements	18
9 Acceptance tests	18
9.1 Laboratory tests.....	18

9.1.1	General	18
9.1.2	Sampling and preparation of samples and test pieces.....	18
9.1.3	Chemical composition.....	18
9.1.4	Microstructure.....	23
9.1.5	Decarburisation	24
9.1.6	Oxide cleanness.....	24
9.1.7	Sulfur prints.....	24
9.1.8	Hardness	24
9.1.9	Tensile tests.....	25
9.1.10	Retest procedures	26
9.2	Dimension tolerances	26
9.2.1	Profile	26
9.2.2	Straightness, surface flatness and twist	27
9.2.3	Cutting and drilling.....	33
9.3	Gauges.....	33
9.4	Inspection for internal quality and surface quality	33
9.4.1	Internal quality.....	33
9.4.2	Surface quality.....	36
9.4.3	Checking of automated testing equipment.....	38
Annex A (normative) Rail profiles.....		49
Annex B (normative) Standard test method for the determination of the plane strain fracture toughness (K_{Ic}) of rails		76
B.1	Test methods.....	76
B.2	Test pieces.....	76
B.3	Number of tests	76
B.4	Test conditions)	76
B.5	Analysis of test data	77
B.6	Reporting of results	77
Annex C (normative) Method for the determination of rail foot surface longitudinal residual stresses.....		82
C.1	Procedure	82
C.2	Strain gauges and their location	82
Annex D (normative) Limiting sulfur prints.....		85
Annex E (normative) Profile and drilling gauges.....		99
Annex F (normative) A_1 Microscopic examination of rail steels using standard diagrams to assess the content of non-metallic inclusions A_1		113
F.1	General	113
F.1.1	Degree of purity	113
F.1.2	Standard diagram plate No. 1	113
F.2	Preparation of specimens.....	113
F.3	Structure and use of standard diagram plate No. 1.....	113
F.3.1	Use of diagram plate No. 1	113
F.3.2	Rating a single inclusion	114
F.3.3	Rating of very small inclusions.....	114
F.4	Test procedure	114
F.4.1	Magnification.....	114
F.4.2	Selection of inclusions	114
F.5	Evaluation.....	115
F.5.1	General	115
F.5.2	Method of evaluation.....	115
F.5.3	Calculation procedure for evaluation using method K.....	115

SS-EN 13674-1:2011+A1:2017 (E)

Annex G (informative) Significant technical changes between this European standard and the previous edition.....	118
Annex ZA (informative) \square_{A1} Relationship between this European Standard and the Essential Requirements of EU Directive 2008/57/EC \square_{A1}.....	120
Bibliography.....	122

European foreword

This document (EN 13674-1:2011+A1:2017) has been prepared by Technical Committee CEN/TC 256 “Railway applications”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 2017, and conflicting national standards shall be withdrawn at the latest by November 2017.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document includes Amendment 1 approved by CEN on 25 December 2016.

This document supersedes A1 EN 13674-1:2011 A1.

The start and finish of text introduced or altered by amendment is indicated in the text by tags A1 A1.

This document has been prepared under a mandate given to CEN/CENELEC/ETSI by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive 2008/57/EC.

For relationship with EU Directive 2008/57/EC, see informative Annex ZA, which is an integral part of this document.

A1 Annex G A1 provides details of significant technical changes between this European Standard and the previous edition.

This part of EN 13674 is the first of the series EN 13674, *Railway applications — Track — Rail*, which consists of the following parts:

- *Part 1: Vignole railway rails 46 kg/m and above;*
- *Part 2: Switch and crossing rails used in conjunction with Vignole railway rails 46 kg/m and above;*
- *Part 3: Check rails;*
- *Part 4: Vignole railway rails from 27 kg/m to, but excluding 46 kg/m.*

Other standards for rails and corresponding welding processes, already published or under preparation, are:

- EN 14587-1, *Railway applications — Track — Flash butt welding of rails — Part 1: New R220, R260, R260Mn and R350HT grade rails in a fixed plant;*
- EN 14587-2, *Railway applications — Track — Flash butt welding of rails — Part 2: New R220, R260, R260Mn and R350HT grade rails by mobile welding machines at sites other than at a fixed plant;*
- prEN 14587-3, *Railway applications — Track — Flash butt welding of rails — — Part 3: Welding in association with crossing construction;*
- EN 14730-1, *Railway applications — Track — Aluminothermic welding of rails — Part 1: Approval of welding processes;*

SS-EN 13674-1:2011+A1:2017 (E)

- EN 14730-2, *Railway applications — Track — Aluminothermic welding of rails — Part 2: Qualification of aluminothermic welders, approval of contractors and acceptance of welds*;
- EN 14811, *Railway applications — Track — Special purpose rail — Grooved and associated construction*;
- EN 15594, *Railway applications — Track — Restoration of rails by electric arc welding*;
- prEN xxxxx, *Railway applications — Track — Forged rail transitions*.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Introduction

This Introduction provides an explanation of the concepts, and reasoning considered for this standard.

Whenever possible this part of EN 13674 is performance based, recognises the European Quality System standard EN ISO 9001 and requires manufacturers to offer the latest proven technology to consistently satisfy the demanding quality of the required product.

This part of EN 13674 has two major divisions:

- 1) qualifying tests;
- 2) acceptance tests.

The qualifying tests take into account performance requirements. They also include typical results from relevant acceptance tests.

The acceptance tests control those characteristics of the rail steel and rail that are of relevance to the production of high quality rails including heat treated rails and the demands of the railway.

To ensure the supply of high quality rails, some restrictions on production processes are considered.

The performance based standard applies to all procurements falling inside the requirements of the European Procurement Directive (93/38/EEC of 14th June 1993), taking into account safety implications and at the same time addressing modern production technology and the requirements of high-speed railways. As a result of the Directive it was recognised that there would be few opportunities (and these would have to be for transparent safety considerations) for derogation from the standard to operate between the user and the manufacturer.

The standard includes a prerequisite for all manufacturers to prove conformity against a set of qualifying test criteria at the time of tendering. The Qualifying tests include all "normal" acceptance test results plus new "type-casting" features such as fracture toughness, fatigue and residual stress. To provide users with the necessary confidence, acceptance limits have been based on results from rail known to have performed well in demanding track installations.

The standard includes a quality assurance and inspection clause as part of product integrity.

In order that quality management systems are consistent across all manufacturers and that users have the best assurance for the consistency of required product quality on this safety critical component of the track, this rail standard recommends that the manufacturers' quality assurance systems are at least equivalent to the requirements of EN ISO 9001. The inclusion of this requirement also reduces the need to incorporate detailed method and calibration descriptions on items such as normal chemical composition determination and the need to define more extensive testing.

SS-EN 13674-1:2011+A1:2017 (E)

1 Scope

This European Standard specifies Vignole railway rails of 46 kg/m and greater linear mass, for conventional and high speed railway track usage.

Nine pearlitic steel grades are specified covering a hardness range of 200 HBW to 440 HBW and include non heat treated non alloy steels, non heat treated alloy steels, and heat treated non alloy steels and heat treated alloy steels.

There are 23 rail profiles specified in this standard.

Two classes of rail straightness are specified, differing in requirements for straightness, surface flatness and crown profile. Two classes of profile tolerances are specified.

2 Normative references

A1 The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies. **A1**

EN 10163-1, *Delivery requirements for surface condition of hot-rolled steel plates, wide flats and sections — Part 1: General requirements*

A1 *deleted text* **A1**

CEN/TR 10261, *Iron and steel — Review of available methods of chemical analysis*

EN 10276-1, *Chemical analysis of ferrous materials — Determination of oxygen in steel and iron — Part 1: Sampling and preparation of steel samples for oxygen determination*

EN ISO 6506-1, *Metallic materials — Brinell hardness test — Part 1: Test method (ISO 6506-1:2005)*

EN ISO 6892-1, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature (ISO 6892-1:2009)*

EN ISO 14284, *Steel and iron — Sampling and preparation of samples for the determination of chemical composition (ISO 14284:1996)*

ISO 1099, *Metallic materials — Fatigue testing — Axial force-controlled method*

ISO 4968, *Steel — Macrographic examination by sulfur print (Baumann method)*

ISO 12108, *Metallic materials — Fatigue testing — Fatigue crack growth method*

ASTM E399, *Standard test method for linear-elastic plane-strain fracture toughness K_{Ic} of metallic materials*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1 heat

liquid steel melt tapped out of a converter or electric arc furnace which includes after continuous casting a given number of blooms relating to the weight of the heat and the extension of the mixing zone. In the case of sequence casting the blooms belonging to the mixing zone should be clearly defined

3.2

sequence

any number of heats, of the same steel grade, which undergo continuous casting in tundishes. Tundishes may be used in parallel if the caster has many strands

3.3

heat treated rail

rail that has undergone accelerated cooling from austenitizing temperature during the metallurgical transformation period

3.4

re-heated rail

rolled rail that has undergone re-austenitization for heat treatment purposes

3.5

mill heat treated rail

heat treated rail that has not undergone re-austenitization after rolling

3.6

rolling process

process between the blooms leaving the heating furnace and exiting the finishing pass

3.7

isothermal treatment process

process whereby blooms are held for a period of time at an elevated temperature for diminishing the hydrogen content

Note 1 to entry: For maximum efficiency this is as near to (but below) the pearlite to austenite transformation temperature as is practically possible.

Note 2 to entry: This process is sometimes referred to as sub critical diffusion annealing.

3.8

qualifying test

special test and criteria which are relevant to some aspects of the service performance of rails. Acceptance tests also form part of the qualifying tests

3.9

acceptance test

test carried out as part of the process and product control system, normally on a heat, sequence or tonnage basis

3.10

rail running surface

curved surface of the rail head. Area between both gauge corners (transition points of the head inclination and the first head radius)

4 Information to be supplied by the purchaser

The purchaser shall provide the supplier with the following information at the time of tender or order:

- a) rail profile (see Annex A);
- b) steel grade (see Clause 5);

SS-EN 13674-1:2011+A1:2017 (E)

- c) profiles class, 'X' or 'Y' (see 9.2.1);
- d) straightness class 'A' or 'B' of rail as specified in 9.2.2;
- e) length(s) of rail (see Table 9);
- f) undrilled or drilled rail ends to take fish bolts, and location and dimensions of holes when required (see 9.2.3);
- g) any special treatment to be applied to bolt holes and corresponding special tolerances for bolt holes (see 9.2.3);
- h) cold stamping on the cut face (see 7.4.3);
- i) paint code requirements (see 7.4.4).

5 Steel grades

The applicable steel grades are given in Table 1. The hardness ranges of the steel grades shall conform to those given in Table 1.

For the steel grades in Table 1, the steel names and steel numbers were allocated in accordance with EN 10027-1 and EN 10027-2, respectively.

Table 1 — Steel grades

Steel grade ^a		Hardness range (HBW)	Description	Branding lines
Steel name	Steel number			
R200	1.0521	200 to 240	Non-alloy (C-Mn) Non heat treated	No branding lines
R220	1.0524	220 to 260	Non-alloy (C-Mn) Non heat treated	-----
R260	1.0623	260 to 300	Non-alloy (C-Mn) Non heat treated	--- -----
R260Mn	1.0624	260 to 300	Non-alloy (C-Mn) Non heat treated	----- -----
R320Cr	1.0915	320 to 360	Alloy (1 %Cr) Non heat treated	----- ----- -----
R350HT	1.0631	350 to 390 ^b	Non-alloy (C-Mn) Heat treated	--- ----- -----
R350LHT	1.0632	350 to 390 ^b	Non-alloy (C-Mn) Heat treated	--- ----- ----- ---
R370CrHT	1.0992	370 to 410	Alloy (C-Mn) Heat treated	--- ----- ----- -----
R400HT	1.1254	400 to 440	Non-alloy (C-Mn) Heat treated	----- ----- -----

^a See Table 5 a) and Table 5 b) for chemical composition/mechanical properties.

^b See Table 6 for hardness requirements.

6 Profile drawings/properties/mass

Rail profiles, dimensions, properties and linear masses shall be in accordance with Annex A. The tolerances of certain dimensions shall be as given in Table 7. All other quantities are informative only.

NOTE Linear masses have been calculated based on the density of steel of 7,85 kg/dm³.

SS-EN 13674-1:2011+A1:2017 (E)

7 Manufacture

7.1 Product integrity

Rails shall be produced under a comprehensive system of factory production control which shall ensure confidence in the conformity of the finished product. The system shall address this European Standard to ensure that the finished products consistently comply with requirements to achieve the product integrity necessary to provide assurance of product safety in track.

Manufacturers shall demonstrate continuing compliance, including documented evidence, with the factory production control system required.

NOTE Manufacturers having a factory production control system which complies with EN ISO 9001 are recognised as satisfying the minimum requirements specified by this clause.

7.2 Blooms

Blooms made from basic oxygen steel or electric arc furnace steel that has been secondary ladle arc refined, vacuum degassed and continuously cast, shall be used for the manufacture of rails.

7.3 Rails

7.3.1 The manufacturer shall operate a procedure for the effective removal of scale during the rolling and straightening processes.

7.3.2 The cross-sectional area of the rail shall not exceed one ninth that of the bloom from which the rail is rolled.

7.3.3 Rail straightening shall be by a two stage roller straightening process which straightens the rail about its XX and YY axes as defined in the rail profiles shown in Annex A. End deviations or a localised deviation on the rail may be corrected using pressing.

NOTE Other mandatory processes are described in the relevant clauses within the standard.

7.4 Identification

7.4.1 Branding

Brand marks shall be rolled in relief on one side and in the middle of the web (see Annex A) of each rail at least once every 4 m. The brand marks on the rails shall be clearly legible and shall be 20 mm to 25 mm high, raised between 0,6 mm and 1,3 mm.

The branding line(s) to denote grade shall be 50 mm in length for the long branding line and 25 mm in length for the short branding line.

The brand marks shall include:

- a) identification of the mill;
- b) steel grade as shown in Table 1;
- c) last two figures of the year of manufacture;
- d) rail profile identification as shown in Annex A.

EXAMPLES

ROLLING MILL _____ 07 60 E1

(60 E1 profile rail rolled 2007, non-alloy rail steel grade R260).

ROLLING MILL _____ 07 60 E1

(60 E1 profile rail rolled 2007, non-alloy heat treated rail steel grade R350HT).

NOTE The sequence of the branding marks is at the discretion of the manufacturer.

7.4.2 Hot stamping

In addition to the branding requirements of 7.4.1 each rail shall be identified by a numerical and/or alphabetical code system, hot stamped on the non-branded side of the rail web by machine and each rail shall be hot stamped at least once every 10 m.

NOTE 1 A rail can display different indications of position of the rail in the bloom (A,B...Y) along its length.

NOTE 2 Subsequent cutting could result in more than one rail length having the same identity.

The figures and letters used shall be clearly legible and shall be 16 mm high. The stamped characters shall have a flat or radius face (1 mm to 1,5 mm wide) with bevels on each side. The letters and numbers shall be on a 10° angle from vertical and shall have rounded corners. The stamping shall be between 0,5 mm and 1,5 mm in depth along the centre of the web. The design shall be as shown in Figure 1.

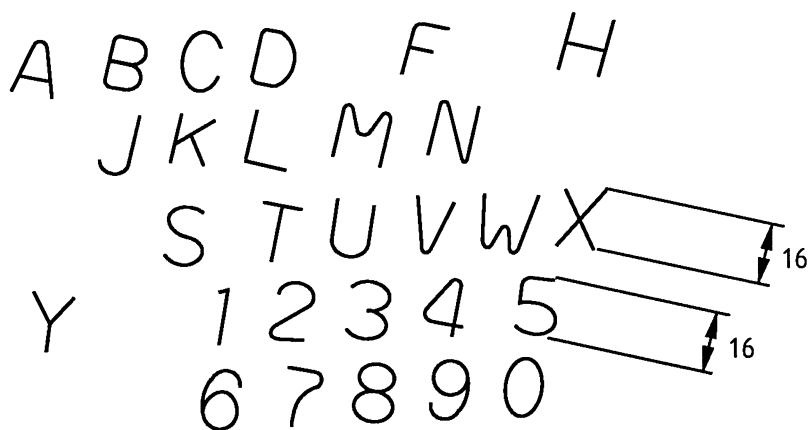


Figure 1 — Design of letters and numbers on a 10° angle for rail stamps

The identification system employed shall be such as to enable the hot stamped marking to be collated with the:

- a) number of the heat from which the rail has been rolled;
- b) number of the strand and position of bloom within the strand;
- c) position of the rail in the bloom (A, B ... Y).

SS-EN 13674-1:2011+A1:2017 (E)

In the event of identification marks having been removed, omitted or requiring alteration, re-identification of such marks shall be made by rotary burr.

7.4.3 Cold stamping

Cold stamping shall only be used on the cut face of the rail within the central portion of the head, at the request of the purchaser.

7.4.4 Other identification

The purchaser shall specify their requirements for any colour coding or special marking instructions and their position on the rail at the time of enquiry or order.

8 Qualifying tests

8.1 Procedure

8.1.1 The manufacturer shall describe any bloom slow cooling or isothermal treatment process used to demonstrate compliance with the requirements of 9.1.3.2.

8.1.2 All qualifying tests as specified in 8.2 to 8.9 shall be undertaken at least once every five years and as a result of any significant production process change for all grades, with the exception of 8.7.1, where predictive equation approval is carried out on an ongoing basis.

The manufacturer shall only carry out testing on the 60E1 profile or the heaviest section produced.

All rail grades and profiles supplied shall conform to the qualifying criteria in accordance with 8.2 to 8.9.

The results for the grades to be supplied shall be provided at the time of tendering.

In the event of a manufacturer not having produced the rail grade prior to the tender enquiry he shall have the option of carrying out such tests on the first available sequence. When the qualifying criteria have been complied with, compliance with the standard is demonstrated and consequently the manufacturer is qualified.

8.1.3 The samples in accordance with 8.1.4 and 8.1.5 shall be removed from finished roller straightened rails. These samples shall not be subject to any further mechanical or thermal treatment (other than the treatment of ageing of the tensile test pieces as described in 9.1.9.2).

8.1.4 Test pieces for fracture toughness, fatigue crack growth rate and fatigue tests (see 8.2, 8.3 and 8.4 respectively) shall be taken from 3 sample rails at least 3 m from the cut ends of the rail. Sample rails shall be from different heats and different strands.

8.1.5 For residual stress tests (see 8.5), there shall be 6 sample rails and the test pieces shall be taken at least 3 m from each rail end.

8.1.6 All tests should be carried out by a laboratory that operates an approved and audited quality assurance system conforming to requirements at least equivalent to EN ISO 9001.

8.1.7 The purchaser shall have access to all test records, calibrations and calculations that contribute to the final results.

8.1.8 All test results shall be reported to the purchaser.

8.2 Fracture toughness (K_{Ic})

8.2.1 Test pieces and test methods

Tests shall be performed in accordance with Annex B.

8.2.2 Qualifying criteria

The value of K_{Ic} shall comply with Table 2.

Table 2 — Minimum single and minimum mean values of K_{Ic}

Steel grade	Minimum single value K_{Ic} (MPa m ^{1/2})	Minimum mean value K_{Ic} (MPa m ^{1/2})
R200 and R220	30	35
R260 and R260Mn	26	29
R320Cr	24	26
R350HT	30	32
R350LHT, R370CrHT, R400HT	26	29

NOTE In some circumstances K_Q^* values can be used for the purpose of qualification, see B.6.

8.3 Fatigue crack growth rate

8.3.1 Test method

Tests shall be carried out in accordance with the general requirements of ISO 12108.

8.3.2 Test pieces

A three point bend, single edge notch test piece, of the dimensions and location within the rail shown in Figure 2 shall be used.

8.3.3 Number of tests and test conditions

A minimum of 3 tests from each sample rail shall be performed under the following conditions:

- test temperature shall be within the range +15 °C to +25 °C;
- $R = 0,5$ ($R =$ minimum cyclic load/maximum cyclic load);
- 3 point bend test piece loading span shall be $4 W$ (see Figure 2);
- cyclic loading frequency shall be within the range 15 Hz to 40 Hz;
- environment: laboratory air.

8.3.4 Qualifying criteria

Fatigue crack growth rates (m/Gc) shall not exceed the values given in Table 3.