

SVENSK STANDARD

SS-EN 2823:2017

Fastställt/Approved: 2017-10-20
Publicerad/Published: 2017-11-08
Utgåva/Edition: 1
Språk/Language: engelska/English
ICS: 49.025.40

Flyg- och rymdteknik – Fiberförstärkt plast – Bestämning av fuktig atmosfärs exponeringseffekt på fysikaliska och mekaniska egenskaper

Aerospace series – Fibre reinforced plastics – Determination of the effect of exposure to humid atmosphere on physical and mechanical characteristics

This preview is downloaded from www.sis.se. Buy the entire standard via <https://www.sis.se/std-8029048>

Standarder får världen att fungera

SIS (Swedish Standards Institute) är en fristående ideell förening med medlemmar från både privat och offentlig sektor. Vi är en del av det europeiska och globala nätverk som utarbetar internationella standarder. Standarder är dokumenterad kunskap utvecklad av framstående aktörer inom industri, näringsliv och samhälle och befrämjar handel över gränser, bidrar till att processer och produkter blir säkrare samt effektiviserar din verksamhet.

Delta och påverka

Som medlem i SIS har du möjlighet att påverka framtida standarder inom ditt område på nationell, europeisk och global nivå. Du får samtidigt tillgång till tidig information om utvecklingen inom din bransch.

Ta del av det färdiga arbetet

Vi erbjuder våra kunder allt som rör standarder och deras tillämpning. Hos oss kan du köpa alla publikationer du behöver – allt från enskilda standarder, tekniska rapporter och standardpaket till handböcker och onlinetjänster. Genom vår webbtjänst e-nav får du tillgång till ett lättnavigerat bibliotek där alla standarder som är aktuella för ditt företag finns tillgängliga. Standarder och handböcker är källor till kunskap. Vi säljer dem.

Utveckla din kompetens och lyckas bättre i ditt arbete

Hos SIS kan du gå öppna eller företagsinterna utbildningar kring innehåll och tillämpning av standarder. Genom vår närhet till den internationella utvecklingen och ISO får du rätt kunskap i rätt tid, direkt från källan. Med vår kunskap om standarders möjligheter hjälper vi våra kunder att skapa verklig nytta och lönsamhet i sina verksamheter.

Vill du veta mer om SIS eller hur standarder kan effektivisera din verksamhet är du välkommen in på www.sis.se eller ta kontakt med oss på tel 08-555 523 00.



Standards make the world go round

SIS (Swedish Standards Institute) is an independent non-profit organisation with members from both the private and public sectors. We are part of the European and global network that draws up international standards. Standards consist of documented knowledge developed by prominent actors within the industry, business world and society. They promote cross-border trade, they help to make processes and products safer and they streamline your organisation.

Take part and have influence

As a member of SIS you will have the possibility to participate in standardization activities on national, European and global level. The membership in SIS will give you the opportunity to influence future standards and gain access to early stage information about developments within your field.

Get to know the finished work

We offer our customers everything in connection with standards and their application. You can purchase all the publications you need from us - everything from individual standards, technical reports and standard packages through to manuals and online services. Our web service e-nav gives you access to an easy-to-navigate library where all standards that are relevant to your company are available. Standards and manuals are sources of knowledge. We sell them.

Increase understanding and improve perception

With SIS you can undergo either shared or in-house training in the content and application of standards. Thanks to our proximity to international development and ISO you receive the right knowledge at the right time, direct from the source. With our knowledge about the potential of standards, we assist our customers in creating tangible benefit and profitability in their organisations.

If you want to know more about SIS, or how standards can streamline your organisation, please visit www.sis.se or contact us on phone +46 (0)8-555 523 00



Europastandarden EN 2823:2017 gäller som svensk standard. Detta dokument innehåller den officiella engelska versionen av EN 2823:2017.

The European Standard EN 2823:2017 has the status of a Swedish Standard. This document contains the official version of EN 2823:2017.

© Copyright/Upphovsrätten till denna produkt tillhör SIS, Swedish Standards Institute, Stockholm, Sverige. Användningen av denna produkt regleras av slutanvändarlicensen som återfinns i denna produkt, se standardens sista sidor.

© Copyright SIS, Swedish Standards Institute, Stockholm, Sweden. All rights reserved. The use of this product is governed by the end-user licence for this product. You will find the licence in the end of this document.

Uppllysningar om sakinnehållet i standarden lämnas av SIS, Swedish Standards Institute, telefon 08-555 520 00. Standarder kan beställas hos SIS Förlag AB som även lämnar allmänna uppllysningar om svensk och utländsk standard.

Information about the content of the standard is available from the Swedish Standards Institute (SIS), telephone +46 8 555 520 00. Standards may be ordered from SIS Förlag AB, who can also provide general information about Swedish and foreign standards.

Har du synpunkter på innehållet i den här standarden, vill du delta i ett kommande revideringsarbete eller vara med och ta fram andra standarder inom området? Gå in på www.sis.se - där hittar du mer information.

EUROPEAN STANDARD

EN 2823

NORME EUROPÉENNE

EUROPÄISCHE NORM

March 2017

ICS 49.025.40

English Version

**Aerospace series - Fibre reinforced plastics -
Determination of the effect of exposure to humid
atmosphere on physical and mechanical characteristics**

Série aérospatiale - Plastiques renforcés de fibres -
Détermination de l'influence de l'exposition à
l'atmosphère humide sur les caractéristiques
mécaniques et physiques

Luft- und Raumfahrt - Faserverstärkte Kunststoffe -
Ermittlung des Einflusses der Auslagerung in feuchtem
Klima auf die mechanischen und physikalischen
Eigenschaften

This European Standard was approved by CEN on 6 February 2017.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

SS-EN 2823:2017 (E)

Contents		Page
European foreword		3
1	Scope.....	4
2	Normative references.....	4
3	Terms and definitions.....	4
4	Methodology	5
5	Apparatus.....	5
6	Specimens.....	5
7	Procedure	7
8	Expression of results.....	10
9	Designation	11
10	Test report.....	11

European foreword

This document (EN 2823:2017) has been prepared by the Aerospace and Defence Industries Association of Europe - Standardization (ASD-STAN).

After enquiries and votes carried out in accordance with the rules of this Association, this Standard has received the approval of the National Associations and the Official Services of the member countries of ASD, prior to its presentation to CEN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2017, and conflicting national standards shall be withdrawn at the latest by September 2017.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

SS-EN 2823:2017 (E)

1 Scope

This European Standard specifies the method for determining the effect of exposure to a humid atmosphere on the physical and mechanical characteristics of fibre reinforced plastics.

This standard applies to all laminates, whatever the nature of the reinforcement and organic matrix used, unless otherwise indicated in the material standard and/or technical specification.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 2743, *Aerospace series — Fibre reinforced plastics — Standard procedures for conditioning prior to testing unaged materials*

EN 2744, *Aerospace series — Non-metallic materials — Preferred test temperatures*

EN 3615, *Aerospace series — Fibre reinforced plastics — Determination of the conditions of exposure to humid atmosphere and moisture absorption* 1)

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

"pilot" specimens

specimens intended to establish the exposure temperature required to achieve an equilibrium condition at the specified humidity level in a limited period of time

3.2

specimens "to be aged"

specimens intended to determine the mechanical and physical characteristics after exposure

3.3

"traveller" specimens

specimens representative of specimens "to be aged" which accompany these in the climatic chamber and are intended to monitor moisture absorption

3.4

equilibrium condition

condition of the material at a specified hygrometry when it has reached constant mass

3.5

constant mass

mass of the specimen obtained after several successive weighings carried out at regular intervals when the difference between weighings is less than a specified value

1) Published as ASD-STAN Prestandard at the date of publication of this standard by AeroSpace and Defence industries Association of Europe - Standardization (www.asd-stan.org)

3.6

as-cured condition

see EN 2743

4 Methodology

The test results obtained with the specimens in the as-cured condition are compared with those obtained with specimens "to be aged" after exposure to the specified humid atmosphere, in accordance with the following procedure:

- a) carry out the mechanical or physical test according to the appropriate standard on specimens in the as-cured condition (see EN 2743A);
- b) using pilot specimens determine the highest possible exposure temperature guaranteeing a behaviour of the material in conformity with Fick's law (reaching an equilibrium condition). This determination shall be carried out at least once for each case of fibre/resin/temperature combination;
- c) expose the specimens "to be aged" to the specified hygrometry and to the temperature as determined above until they reach the equilibrium condition. Traveller specimens shall be permanently subjected to the same exposure conditions;
- d) carry out the mechanical or physical tests according to the applicable standards.

NOTE 1 In the preparation of this standard both Langmuir model and Fick's law were considered. While acknowledging that Langmuir Models more exact, Fick's law will be used to define equilibrium conditions in composite materials.

A temperature of 70 °C is chosen as the initial verification temperature in order to achieve a reasonable rate of moisture pick-up. If the pilot specimens results suggest a significant deviation from Fick's law then a lower temperature should be selected.

5 Apparatus

5.1 Climatic chamber capable of keeping the specified temperature to within ± 1 °C and relative humidity to within ± 3 %.

5.2 Desiccator.

5.3 Balance accurate to within 0,1 mg.

5.4 Air circulating oven capable of keeping the specified temperature to within ± 5 °C.

5.5 Clean and dry absorbent cloth or filter paper.

5.6 Sealed container: metallized polythene bag or airtight metal or glass enclosure.

6 Specimens

All the aspects of the manufacturing process (in particular the surface finish) influence the test results.

SS-EN 2823:2017 (E)

6.1 Pilot specimens

The panels intended to make up the pilot specimens shall be symmetrically arranged in layers:

- unidirectional preimpregnates: unidirectional (0°) or crossed (0°/90°) lay-up;
- fabrics: all plies warpwise in the same direction.

The dimensions of the pilot specimens shall be in conformity with Figure 1 and Table 1.

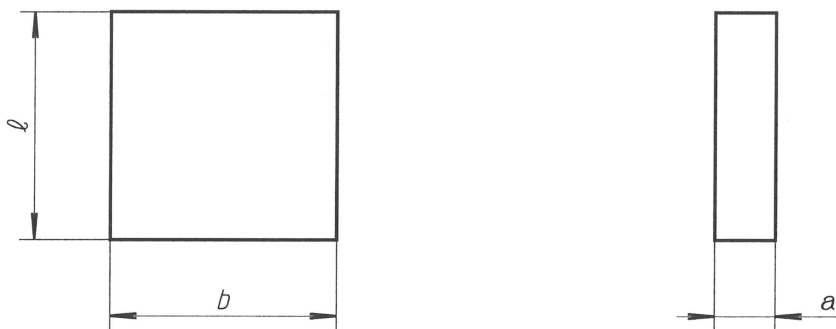


Figure 1

Table 1

Dimensions in millimetres

<i>l</i>	75 ± 1
<i>b</i>	75 ± 1
<i>a</i>	the lowest possible

6.2 Specimens "to be aged" (specimens for mechanical and physical tests)

The shape, dimensions and manufacturing procedure for the specimens are specified in the material standard or test method.

They shall be in their final form, for example, machined, drilled, tabbed, etc.

6.3 Traveller specimens

A minimum of three traveller specimens, taken from the same panel as the specimens "to be aged", but without tabs, holes, etc. shall be used.

The traveller specimens shall be rectangular or square, their length and width equal to or greater than 25 mm and their mass greater than 1,5 g.

The quality of the faces and edges shall be identical to that of the ageing specimens.

7 Procedure

7.1 Conditioning before exposure

Specimens to be aged shall not undergo any special conditioning, a condition of equilibrium being the only criterion sought.

7.2 Exposure conditions

7.2.1 The humidity level shall be specified.

Standard condition: $\left(85 \begin{smallmatrix} +5 \\ -1 \end{smallmatrix}\right)\%$

Optional: $\left(95 \begin{smallmatrix} +5 \\ -1 \end{smallmatrix}\right)\%$

7.2.2 Determination of exposure temperature

It shall be determined on the pilot specimens according to the following procedure:

- expose a pilot specimen to the exposure temperature of (70 ± 2) °C;
- check that the condition of equilibrium has been reached (see 7.2.3) at this temperature;
- if this is not the case, expose a new pilot specimen to a lower temperature chosen from EN 2744;
- check that the condition of equilibrium has been reached (see 7.2.3) at this new temperature;
- if this is not the case, redo the procedure until a temperature is determined whereby the condition of equilibrium is reached.

NOTE 1 If the condition of equilibrium is reached at 70 °C, a higher exposure temperature may be sought, chosen from EN 2744.

NOTE 2 This operation may be replaced by a continuous weighing (thermobalance type setup) of the pilot specimen in a humid atmosphere.

7.2.3 Determination of the condition of equilibrium

The total period of exposure for all specimens shall be continued until they reach the equilibrium condition.

Constant mass is achieved for test specimens of a thickness of $(2 \pm 0,2)$ mm when the difference between three successive weighings carried out at an interval of 168 h on traveller specimens (see figure 2) and in conformity with the formula below:

$$\frac{|M_{j-2} - M_j|}{M_j} \leq 5 \times 10^{-4}$$

where

M_j represents the mean weights of the travellers specimens at the time t_j .